


| | |
|--------------------------------------|------------------|
| SPECIFICATION CONTROL DRAWING | 7726S0LL4 |
|--------------------------------------|------------------|

| | | | |
|-----------------|---|----------|----------|
| CHEMINAX | 77 OHM, AWG 26, 19 STRANDS OF AWG 38, DATA BUS, MIL-STD-1553, LOW FLUORIDE, OUTER SPACE USE | Date | 12-31-08 |
| | | Revision | C |

THIS SPECIFICATION SHEET FORMS A PART OF THE LATEST ISSUE OF RAYCHEM SPECIFICATION 1200.

| | |
|-----------------------------|-----------------------------------|
| CONSTRUCTION DETAILS | ELECTRICAL CHARACTERISTICS |
|-----------------------------|-----------------------------------|

DIMENSIONS ARE NOMINAL VALUES IN INCHES UNLESS OTHERWISE DESIGNATED.

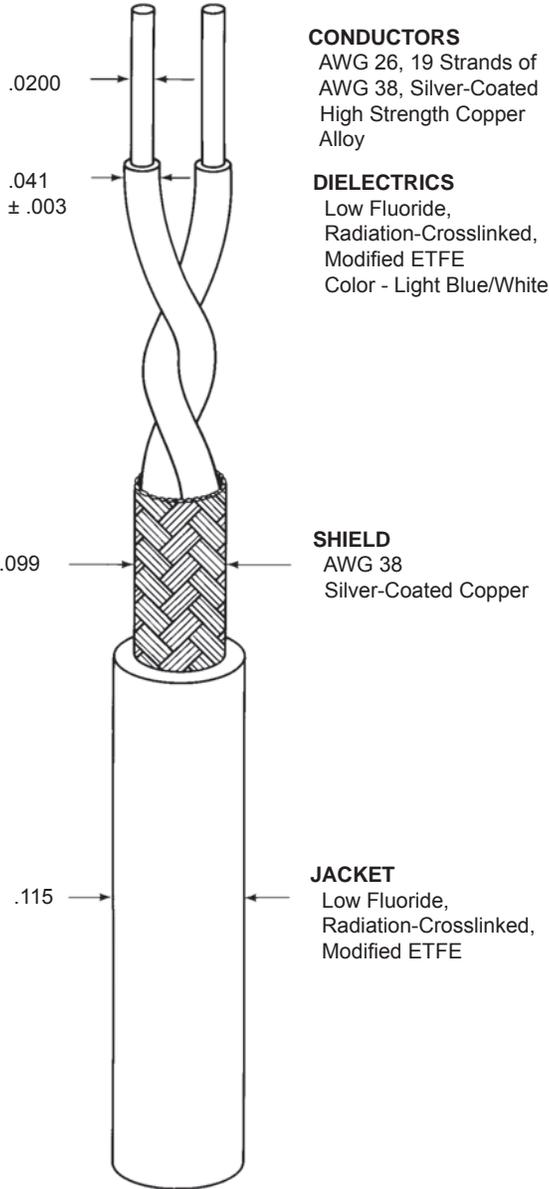

| | |
|--------------------------|-----------------------------------|
| CHARACTERISTIC IMPEDANCE | 77 ± 5 ohms, Method C at 1 MHz |
| MUTUAL CAPACITANCE | 30.0 pF/ft. (maximum) |
| ATTENUATION | 1.5 dB/100 ft. (maximum) at 1 MHz |

| |
|--------------------------------|
| ADDITIONAL REQUIREMENTS |
|--------------------------------|

| | |
|---|--|
| FLUORIDE EXTRACTION (Dielectrics prior to cabling; and Jacket - per Raychem Spec 55/) | 70 ± 2°C for 168 hours, 20 ppm (maximum) |
|---|--|

| |
|--|
| COMPONENT WIRE PRIOR TO CABLING (Test Procedures per SAE AS22759) |
|--|

| | |
|------------------------------------|--|
| CROSSLINK PROOF | 300 ± 3°C for 1 hour, .500 inch mandrel, .375 lb., 2.5 kV dielectric test |
| INSULATION (DIELECTRIC) ELONGATION | 50% (minimum) |
| TENSILE STRENGTH | 5000 lbf/in ² (minimum) |
| INSULATION FLAWS | |
| SPARK TEST | 3.0 kV (rms) |
| IMPULSE TEST | 8.0 kV (peak) |
| INSULATION RESISTANCE | 5000 megohms for 1000 ft. (minimum) |
| LOW TEMPERATURE-COLD BEND | -65 ± 3°C for 4 hours, .500 inch mandrel, .500 lb., 2.5 kV dielectric test |
| SHRINKAGE | 200 ± 3°C for 1 hour, .125 inch (maximum) in 12 inches |

| |
|---|
| FINISHED CABLE (Test Procedures per NEMA WC 27500, unless otherwise specified) |
|---|

| | |
|--------------------------------------|--|
| BLOCKING | 200°C for 6 hours |
| CABLE LAY LENGTH | .75 inch (minimum), 1.25 inches (maximum) |
| CROSSLINKED VERIFICATION | 300 ± 5°C for 6 hours, 3.00 inch mandrel |
| FLAMMABILITY (Method B of Spec 1200) | 3 seconds (maximum); 3 inches (maximum); no flaming of facial tissue |
| JACKET ELONGATION | 50% (minimum) |
| TENSILE STRENGTH | 5000 lbf/in ² (minimum) |
| JACKET FLAWS | |
| SPARK TEST | 1.0 kV (rms) |
| IMPULSE TEST | 6.0 kV (peak) |
| JACKET THICKNESS | .008 inch (nominal) |
| LOW TEMPERATURE-COLD BEND | -55 ± 5°C for 4 hours, 3.00 inch mandrel |
| SHIELD COVERAGE | 90% (minimum) |
| VOLTAGE WITHSTAND (DIELECTRIC) | 1500 volts (rms) |
| WEIGHT | 9.7 lbs/1000 ft. (nominal) |

| |
|---------------------------------|
| OUTER SPACE REQUIREMENTS |
|---------------------------------|

| | |
|-------------------------------------|--|
| RADIATION RESISTANCE | 500 megarads/3.50 inch mandrel 1.0 kV dielectric test |
| VACUUM STABILITY | |
| TOTAL MASS LOSS (TML) | 1.00% (maximum) |
| VOLATILE CONDENSABLE MATERIAL (VCM) | 0.10% (maximum) |
| WEIGHT LOSS (Test per Spec 55/) | 0.45% (maximum) |

Outer jacket color will be white (designated by a "-9" appended to the part number, e.g. 7726S0LL4-9) unless otherwise specified.

Designate outer jacket color with a dash number in accordance with MIL-STD-681. Other codes and suffixes may be added to the part number, as necessary, to capture any additional requirements imposed by the purchase order.

Users should evaluate the suitability of this product for their application. Specifications are subject to change without notice. Tyco Electronics also reserves the right to make changes in materials or processing, which do not affect compliance with any specification, without notification to Buyer.